

County Highways Laboratory

Stockbridge Road, Micheldever Station, Hampshire, SO21 3BB

Telephone:01962 774502

email: CountyHighwaysLab@hants.gov.uk

**Hampshire**
County Council

Client: L & S Waste Mangement Ltd Pegham Industrial Estate
Laveys Lane
Fareham
Hampshire
PO15 6SD

Lab No.: A0365

F.A.O: Steve Kew


Particle Size Distribution Report

Project: Aggregate testing: L & S April 2022
Location: Type 1 Stock
Material: Crushed Granite/Limestone
Specification: SHW Clause 803 Type 1 Subbase
Contractor: N/A
Supplier/Plant: STOCKPILE
Date Sampled: 06/04/2022
Sampled by: JH
Sample Type: Bulk
Test Mass (g): 21468

Date Received: 06/04/2022
Tested by: MB
Date Tested: 25/04/2022
Site Ref.: JH6

Test method: BS EN 933-1: 2012 Sampling Method: BS EN 932-1:1997
Preparation Method: BS EN 932-2: 1999

Sieve Size (mm)	Percent passing	Specification
63	100	100.0
31.5	96	75.0 - 99.0
16	52	48.0 - 78.0
8	29	27.0 - 57.0
4	21	13.0 - 43.0
2	16	10.0 - 36.0
1	13	8.0 - 28.0
0.063	6.4	<= 9.0

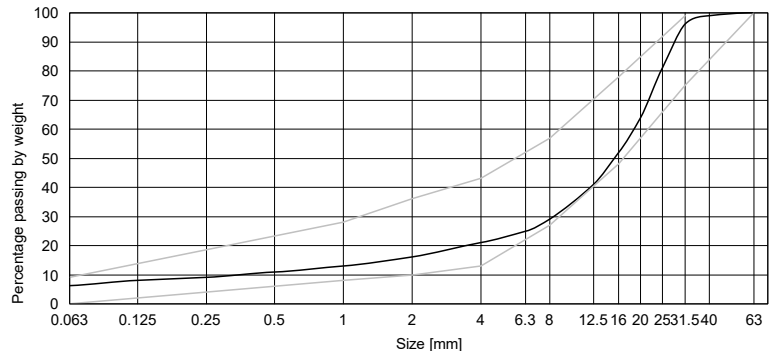

Moisture content (%) 2.1
Uniformity Coefficient 51

Requirements on specific size fractions

Size fraction	% pass	Specification	Complies (Spec)
4/8	8	7 - 30	yes
8/16	23	7 - 30	yes



0645

Remarks The sample complies with the specification

Signed	
Date	05/05/2022
Approved	E. Frost

note: County Highways Laboratory only accepts responsibility for the accuracy of the results contained in this report. No responsibility can be accepted for the results being representative of the material or items sampled unless sampling has been carried out by County Highways Laboratory staff. This result may not be reproduced either in part or in full without the written permission of the County Highways Laboratory. The results stated in this report are only related to the items tested. For samples taken by the Client the results stated in this report are only related to the sample/s as received.